

Research



Cite this article: Vasiljevic ZZ, Dojcinovic MP, Vujancevic JD, Jankovic-Castvan I, Ognjanovic M, Tadic NB, Stojadinovic S, Brankovic GO, Nikolic MV. 2020 Photocatalytic degradation of methylene blue under natural sunlight using iron titanate nanoparticles prepared by a modified sol–gel method. *R. Soc. Open Sci.* **7**: 200708. <http://dx.doi.org/10.1098/rsos.200708>

Received: 29 April 2020

Accepted: 4 August 2020

Subject Category:

Chemistry

Subject Areas:

environmental chemistry/nanotechnology/
materials science

Keywords:

dye wastewater, photocatalytic degradation,
methylene blue dye, sol–gel method,
iron titanate

Author for correspondence:

Z. Z. Vasiljevic

e-mail: zorka.djuric@itn.sanu.ac.rs

This article has been edited by the Royal Society of Chemistry, including the commissioning, peer review process and editorial aspects up to the point of acceptance.

Electronic supplementary material is available online at <https://doi.org/10.6084/m9.figshare.c.5105934>.

Photocatalytic degradation of methylene blue under natural sunlight using iron titanate nanoparticles prepared by a modified sol–gel method

Z. Z. Vasiljevic¹, M. P. Dojcinovic², J. D. Vujancevic¹,
I. Jankovic-Castvan³, M. Ognjanovic⁴, N. B. Tadic⁵,
S. Stojadinovic⁵, G. O. Brankovic² and M. V. Nikolic²

¹Institute of Technical Sciences of SASA, Belgrade, Serbia

²Institute for Multidisciplinary Research, ³Faculty of Technology and Metallurgy, ⁴Institute of Nuclear Sciences Vinca, and ⁵Faculty of Physics, University of Belgrade, Belgrade, Serbia

ZZV, 0000-0002-7817-8648

The aim of this work was to synthesize semiconducting oxide nanoparticles using a simple method with low production cost to be applied in natural sunlight for photocatalytic degradation of pollutants in waste water. Iron titanate (Fe₂TiO₅) nanoparticles with an orthorhombic structure were successfully synthesized using a modified sol–gel method and calcination at 750°C. The as-prepared Fe₂TiO₅ nanoparticles exhibited a moderate specific surface area. The mesoporous Fe₂TiO₅ nanoparticles possessed strong absorption in the visible-light region and the band gap was estimated to be around 2.16 eV. The photocatalytic activity was evaluated by the degradation of methylene blue under natural sunlight. The effect of parameters such as the amount of catalyst, initial concentration of the dye and pH of the dye solution on the removal efficiency of methylene blue was investigated. Fe₂TiO₅ showed high degradation efficiency in a strong alkaline medium that can be the result of the facilitated formation of OH radicals due to an increased concentration of hydroxyl ions.

1. Introduction

The major worldwide challenge for the twenty-first century is to supply and ensure safe water for the entire ecosystem. Rapid industrialization growth is the major cause of water pollution. Dyes are a class of organic compounds, widely used in textiles, printing and food industry. Dye effluents have a considerable negative influence on the environment, and most of them are highly toxic and non-biodegradable [1,2]. Methylene blue (MB) is a phenothiazine derivative, used for dyeing textiles, and it is highly toxic and carcinogenic [3]. Conventional methods like adsorption, ozonation, etc., have been used for removing these highly toxic compounds; however, due to different limitations, these pollutants cannot be eliminated from waste water [4]. Advanced oxidation processes (AOPs) are a class of oxidation techniques in which organic contaminants are degraded to harmless products. Namely, in this process, $\cdot\text{OH}$ radicals produced *in situ*, initiate oxidation reactions ending with complete mineralization of CO_2 and H_2O [5,6]. In this regard, semiconductor photocatalysis is a promising technique for the degradation of organic pollutants. There are several reasons why using semiconductors as activators in AOPs has an advantage: (i) they are low-cost and non-toxic; (ii) their electronic and optical properties can be modified by size reduction, doping or sensitizers; (iii) the multi-electron transfer process is facilitated; and (iv) they are recyclable without substantial loss in photocatalytic activity [5,7]. TiO_2 has been extensively investigated as a photocatalyst for the decomposition of organic pollutants [8,9]. Despite its good chemical stability and low production cost, one major difficulty using this photocatalyst is its large band gap limiting photocatalytic activity in the visible-light region. Thus, it is necessary to develop materials which will absorb in the visible-light regime and prevent electron–hole recombination. Haematite (Fe_2O_3) with a band gap of 2.1–2.2 eV, is also a promising material for use in photocatalysis due to its ability to absorb light up to 600 nm, high stability in an oxidative environment, abundance and low-cost fabrication [10]. However, due to low conductivity and short hole diffusion length, its photocatalytic performance is still limited [11,12]. Iron titanate (Fe_2TiO_5), a hybrid of TiO_2 and Fe_2O_3 , is a narrow band gap (E_g approx. 2.2 eV) semiconductor absorbing in the visible-light spectrum, similar to Fe_2O_3 . It is an inexpensive, non-toxic material with high chemical stability. Additionally, its electronic and atomic structures are similar to TiO_2 [13,14], thus recombination of photo-generated electrons and holes could be suppressed facilitating transport to hydroxyl groups on the particle surface [15].

In this study, Fe_2TiO_5 nanoparticles were synthesized by a modified sol–gel method and we have performed a detailed characterization of their structure, morphology, texture and chemistry, optical and electronic properties. The photocatalytic activity of prepared Fe_2TiO_5 nanoparticles was evaluated by the degradation of a cationic dye—methylene blue (MB) exposed to 4 h of natural sunlight. Several operating parameters, such as dose of photocatalyst and the initial pH of the solutions, were also evaluated.

2. Materials and methods

2.1. Reagents and materials

Methylene blue, iron(III) nonahydrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ ACS reagent, purity greater than or equal to 98%), titanium isopropoxide—($\text{Ti}(\text{OCH}(\text{CH}_3)_2)$ purity 98%) oxalic acid (Puriss, purity greater than or equal to 99%) and cetyltrimethylammonium bromide (CTAB, purity greater than or equal to 98%) were purchased from Sigma Aldrich (Merck, Darmstadt, Germany). All chemicals were used as received, without further purification.

2.2. Synthesis of iron titanate nanoparticles

Fe_2TiO_5 nanoparticles were synthesized by a modified sol–gel method using $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ and $\text{Ti}(\text{OCH}(\text{CH}_3)_2)$ as starting reagents, oxalic acid as a chelating agent and CTAB as a surfactant. Details of the synthesis procedure are described in [16]. The obtained powder was calcined at 750°C for 3 h to obtain the desired Fe_2TiO_5 nanoparticles.

2.3. Characterization

The prepared sample was characterized by various techniques. The morphology was examined by transmission electron microscopy (TEM) and field emission electron microscopy (FESEM) on JEM-2100

200 kV (Japan) and TESCAN MIRA3 XM (Czech Republic) devices, respectively. The crystal structure and phase identification were investigated by X-ray diffraction (XRD) analysis using Ni-filtered Cu $K\alpha$ radiation with the wavelength of 1.54178 Å, in the range of $2\theta = 10 - 90^\circ$, with the step of 0.05 s and acquisition rate of 1° min^{-1} on a Rigaku Ultima IV diffractometer (Japan). Fourier transform infrared (FT-IR) spectra were recorded on an FT-IR Nicolet 6700 ATR device (Thermo Fisher, UK) in the range 400–4000 cm^{-1} . UV-vis diffuse reflectance spectra (DRS) were measured on a Shimadzu UV-2600 device with an ISR2600 Plus Integrating sphere attachment (Japan) in the measuring range 200–1400 nm.

Photoluminescence spectra at room temperature were measured on a Horiba Jobin Yvon Fluorolog FL3–22 spectrofluorometer (Japan), using a xenon 450 W lamp as the light source. It was coupled to a double grating monochromator in a wavelength range 220–600 nm. Emission spectra were measured using a double grating monochromator in the 350–650 nm range and side-on photomultiplier (Hamamatsu, model 928P, Japan). The measured spectra were corrected for the spectral response of the measuring system and spectral distribution of the xenon lamp.

Zeta potential and particle size by dynamic light scattering (DLS) at $25 \pm 0.1^\circ\text{C}$ were determined for a 0.1 mg ml^{-1} suspension of Fe_2TiO_5 powder dispersed ultrasonically in deionized water and measured in a disposable zeta cell (DTS 1070) of a NanoZS90 (Malvern, UK) device with a 4 mW He-Ne laser source ($\lambda = 633 \text{ nm}$). The pH was varied between 3 and 12 by adding 0.1 M aqueous solutions of HCl and NaOH. Samples were measured after 1 h of equilibrium time at a constant ionic strength of 0.01 M set by NaCl. All measurements were performed at a given kinetic state followed by a minute of relaxation. The average value of the hydrodynamic diameter was calculated as the number weighted size from fits of the correlation functions.

The specific surface area (SSA) and the porous properties of the photocatalyst were determined based on N_2 adsorption–desorption isotherms measured using a Micromeritics ASAP 2020 instrument (USA). Samples were degassed at 150°C for 10 h under reduced pressure. SSA of samples was calculated according to the Brunauer–Emmett–Teller (BET) method from the linear part of the nitrogen adsorption isotherm. The total pore volume (V_{tot}) was given at $p/p_0 = 0.998$. The volume of the mesopores was calculated according to the Barrett–Joyner–Halenda method from the desorption branch of the isotherm. The volume of micropores was calculated from the alpha-S plot.

2.4. Photocatalytic experiments

The photocatalytic activity of Fe_2TiO_5 nanoparticles was evaluated by the photodegradation of methylene blue (MB) aqueous solution under direct solar radiation in July 2019 between 10.00 and 14.00, where the average daily temperature was $31 \pm 2^\circ\text{C}$. Before irradiation, the solutions were magnetically stirred in dark for 60 min to achieve adsorption–desorption equilibrium between photocatalyst and pollutant. A stock solution of 1000 mg l^{-1} MB was prepared by dissolving MB in 1 l of distilled water. Different amounts of Fe_2TiO_5 catalyst (10, 30 and 50 mg l^{-1}) were tested for the degradation of MB solution. Samples were collected in appropriate time intervals (up to 4 h) and were centrifuged to remove the catalyst. The removal of MB was determined based on the absorption at 662 nm by using a UV–vis spectrophotometer. Then, the absorption was converted to the concentration through the standard calibration curve.

3. Results and discussion

3.1. Iron titanate structure

Figure 1a shows the measured XRD pattern of the obtained Fe_2TiO_5 powder. Structural parameters were refined using the Rietveld method and the GSAS II software package [18]. Pseudobrookite was refined assuming the $Cmcm$ (D_{2h}^{17}) space group starting with a random distribution of TiO_6 and FeO_6 octahedra, where 67% iron ions are both in 4c and 8f sites of the FeO_6 octahedra [19]. As starting unit cell parameters, we used the values previously determined for Fe_2TiO_5 nanocrystalline powder obtained by solid-state synthesis [20]. All diffraction peaks can be indexed to the orthorhombic phase of Fe_2TiO_5 with space group D_{2h}^{17} ($Cmcm$) without any peaks originating from impurities. The Williamson–Hall method [21] was applied to estimate the crystallite size of Fe_2TiO_5 powder as 48.77 nm with a positive tensile strain of 0.00108. The determined unit cell parameters and atomic positions are given in table 1. Refinement of ion occupancy showed that differing from the previously obtained fully disordered structure [19] iron ions showed a slight preference for 4c sites occupying

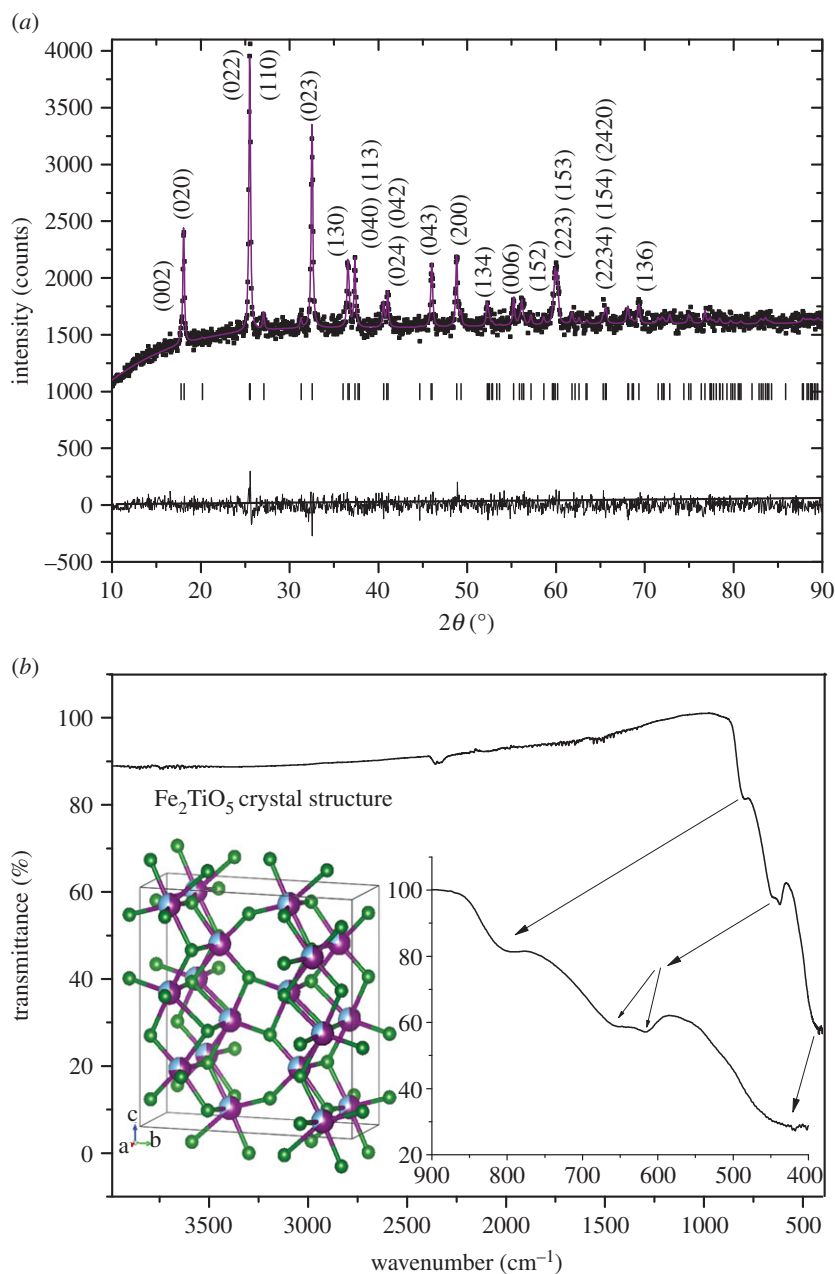


Figure 1. X-ray diffraction pattern of synthesized Fe_2TiO_5 nanocrystalline powder and Rietveld analysis (a) and FT-IR transmittance spectrum of Fe_2TiO_5 nanocrystalline powder; inset: crystal structure was drawn using VESTA [17] (b).

72%, while 64% iron ions are on 8f sites. Such an iron preference was previously noted by Guo *et al.* [22] of 72% and Rodrigues *et al.* [23] of 75%. The crystal structure drawn using these parameters and the VESTA software package [17] is shown as an inset in figure 1b composed of randomly distributed TiO_6 and FeO_6 octahedra. Ti ions are blue (one third), iron ions are purple (two thirds) parts of the balls in the polyhedra representing metal ions, while green are oxygen ions.

Structural properties such as the vibrational frequency of the bonds in Fe_2TiO_5 were further characterized by FT-IR spectroscopy (figure 1b). In our measured spectra, we can note only peaks originating from Fe_2TiO_5 , at approximately 425, 615, 655 and 800 cm^{-1} representing vibrations of Fe–O and Ti–O bonds [24–27].

3.2. Morphology

The Fe_2TiO_5 powder particle size and morphology was examined by FESEM and TEM. The FESEM image shown in figure 2a reveals that Fe_2TiO_5 powder consisted of relatively uniformly sized

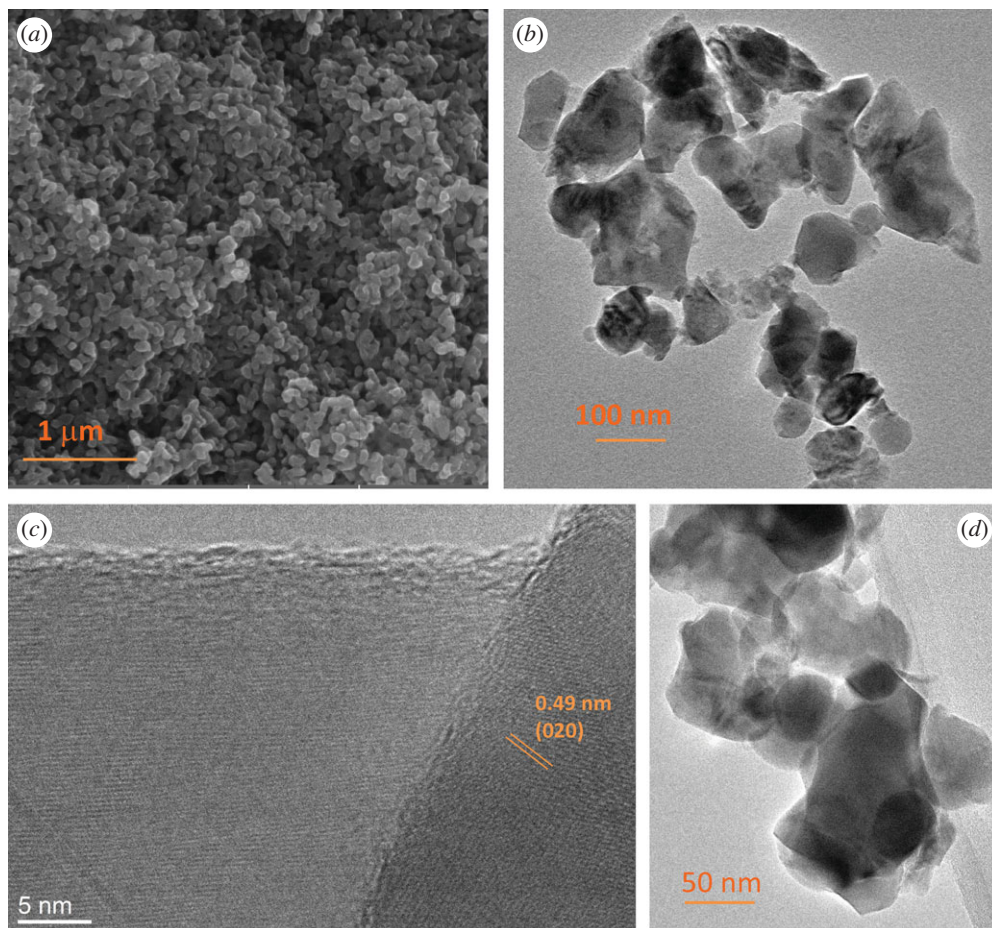


Figure 2. FESEM, magnification 50 000 (a), TEM images (b) magnification 25 000, (d) magnification 50 000 and HRTEM and FFT images (c) magnification 500 000 of Fe_2TiO_5 powder.

Table 1. Unit cell parameters and atomic positions determined for Fe_2TiO_5 , $wR = 2.987\%$.

pseudobrookite (Fe_2TiO_5)						
space group $Cmcm$, $a = 3.73055(28)$, $b = 9.7927(12)$, $c = 9.9766(10)$ Å;						
crystallite size 48.77 nm, microstrain 1937.2, ($wR = 2.797\%$)						
atom	site	x	y	z	occupancy	U_{iso}
Fe_1	8f	0.00000	0.1388(11)	0.5667(13)	0.64	0.012(5)
Ti_1	8f	0.00000	0.1388	0.5667	0.36	0.012
Fe_2	4c	0.00000	0.1875(13)	0.25000	0.72	0.008(8)
Ti_2	4c	0.00000	0.1875	0.25000	0.28	0.008
O_1	4c	0.00000	0.757(5)	0.25000	1.000	0.011(18)
O_2	8f	0.00000	0.050(3)	0.117(3)	1.000	0.015(13)
O_3	8f	0.00000	0.319(4)	0.084(4)	1.000	0.046(12)

nanoparticles with a rhombic shape ranging from 28 to 83 nm and average diameter determined from 72 particles in TEM images of $49.7 \text{ nm} \pm 12.6$ (standard deviation). This morphology was confirmed by TEM (figure 2*b,d*), showing that the Fe_2TiO_5 powder had a rhombic-shaped morphology and different sized agglomerates consisting of smaller particles. This could be due to the coalescence of small particles into agglomerates [28,29]. Analysis of periodic lattice fringes in the high-resolution transmission electron microscopy (HRTEM) image shown in figure 2*c* was performed using a fast Fourier transform (FFT). The calculated FFT patterns enabled the determination of the lattice spacing

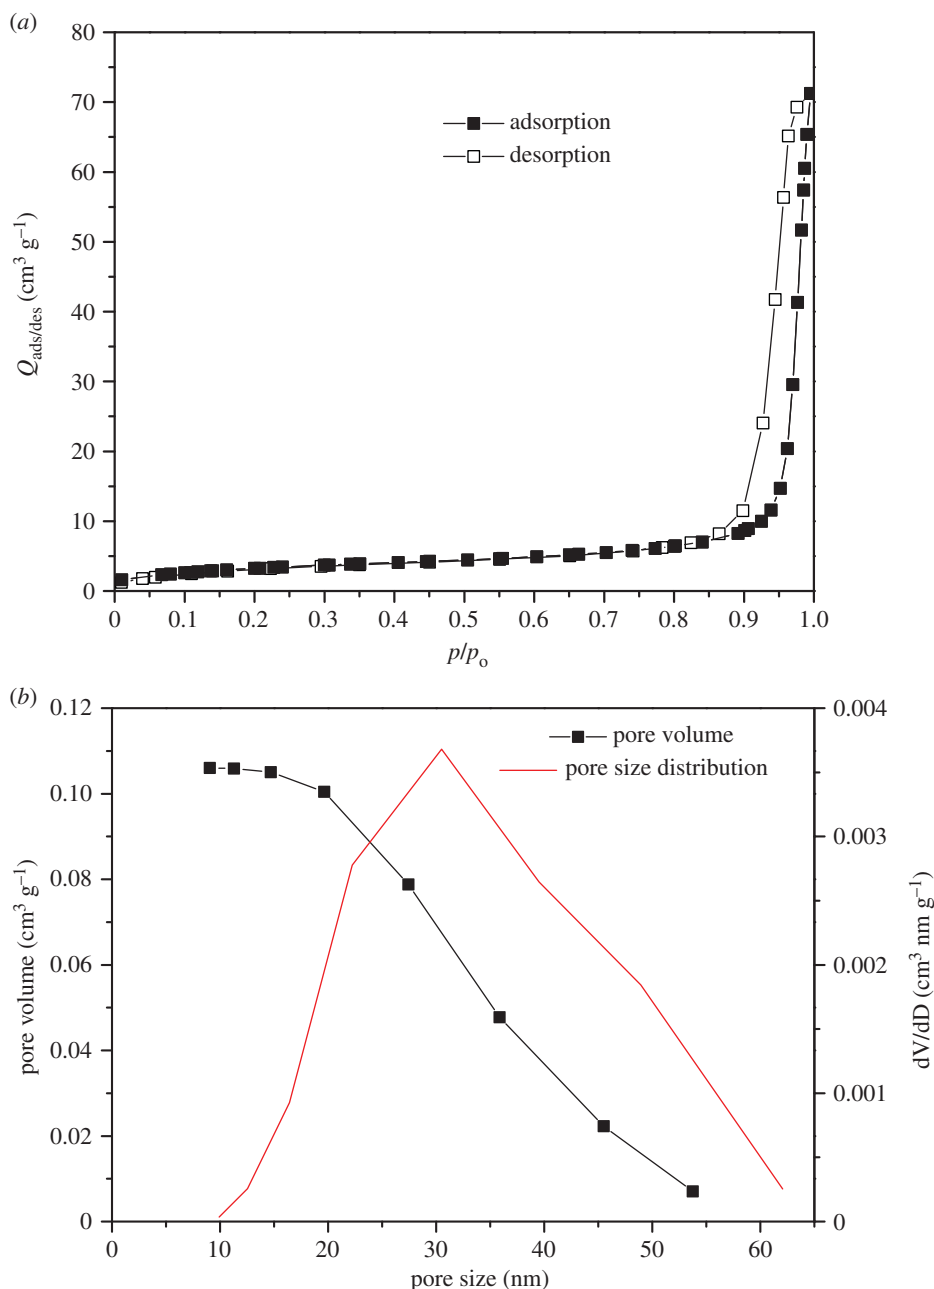


Figure 3. Nitrogen adsorption–desorption isotherms (a) and BET pore size distribution curves (b) for Fe₂TiO₅ powder.

Table 2. Textural properties for the Fe₂TiO₅ powder.^a

sample	S_{BET} (m ² g ⁻¹)	V_{tot} (cm ³ g ⁻¹)	V_{meso} (cm ³ g ⁻¹)	V_{micro} (cm ³ g ⁻¹)	D_{av} (nm)	D_{max} (nm)
Fe ₂ TiO ₅	11.8	0.1072	0.1060	0.0035	31.0	30.5

^aIncludes S_{BET} —BET specific surface area, V_{tot} —total volume of the pores, V_{meso} —volume of the mesopores, V_{micro} —volume of the micropores, D_{av} —the mean pore diameter, D_{max} —diameter of the pores occupying the greatest portion of the volume.

of 0.49 nm (marked in figure 2c) that corresponds to the (020) plane of an orthorhombic *Cmcm* Fe₂TiO₅ structure in accordance with the parameters determined by Rietveld analysis of the measured X-ray diffraction pattern.

3.3. Texture

Figure 3a shows the N₂ adsorption–desorption isotherm of Fe₂TiO₅ powder. According to the IUPAC nomenclature [30], the shape of the nitrogen isotherm could be considered to be a type V isotherm,

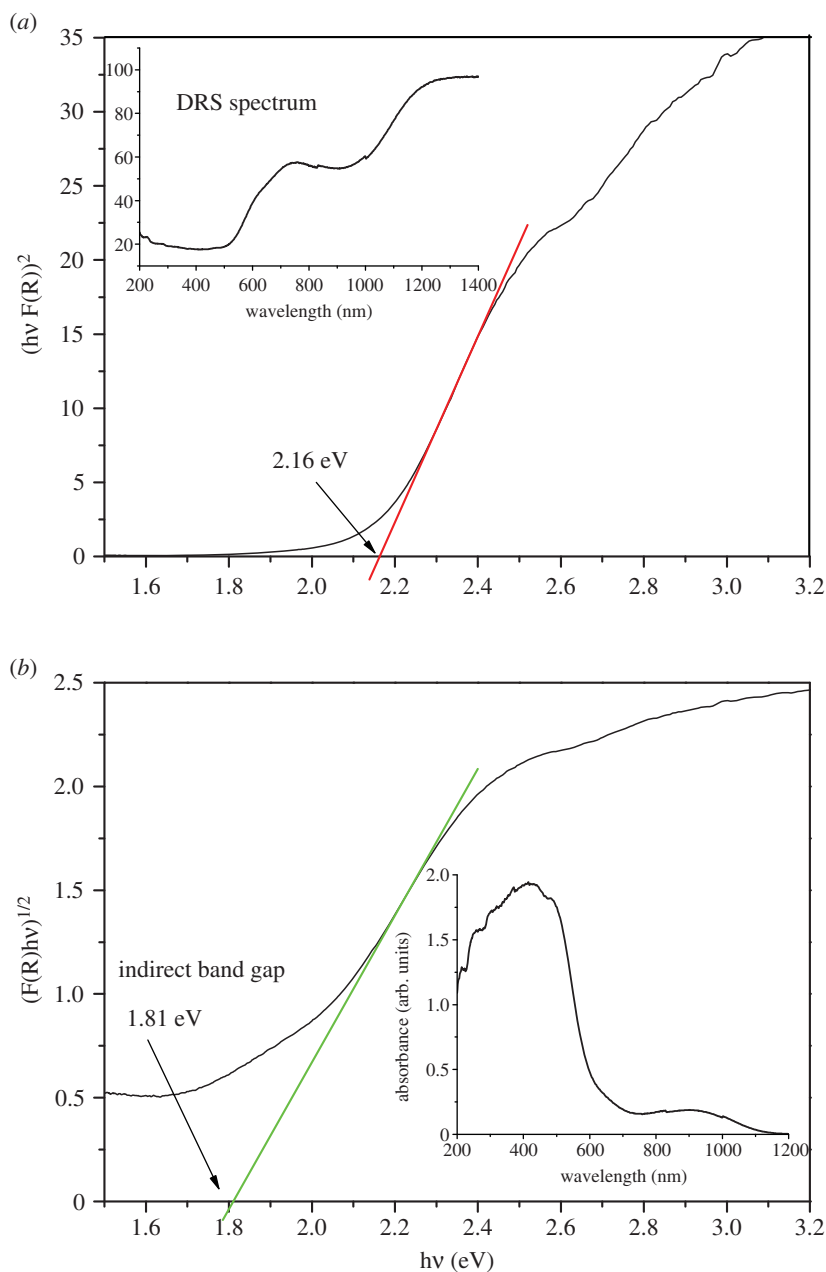


Figure 4. Tauc plot for estimation of direct (a) and indirect (b) band gaps of Fe_2TiO_5 powder; measured diffuse reflectance spectrum, inset (a), absorbance obtained by Kubelka–Munk approximation, inset (b).

which is typical for mesoporous materials. N_2 adsorption–desorption isotherm data for Fe_2TiO_5 powder are depicted in table 2. The specific surface area of the examined sample was $11.8 \text{ m}^2 \text{ g}^{-1}$ and the total pore volume was found to be $0.1072 \text{ cm}^3 \text{ g}^{-1}$. The presence of mesopores [31] with pore diameters ranging from 10 to 60 nm and D_{max} approximately 30.5 nm (figure 3b) was confirmed from pore size distribution analysis.

3.4. Band gap

The measured diffraction reflection spectrum (DRS) of Fe_2TiO_5 powder is shown as an inset in figure 4a. It can be seen that Fe_2TiO_5 nanoparticles have strong visible-light absorption. The equivalent absorption coefficient was calculated using the Kubelka–Munk function and is shown as an inset in figure 4b. Tauc plots for a direct (figure 4a) and indirect (figure 4b) system [32] enabled estimation of the optical band gap values using the relationship of Davis and Mott [33]. Direct and indirect band gap values were estimated as 2.16 and 1.81 eV, respectively. These are similar to some previously obtained values for

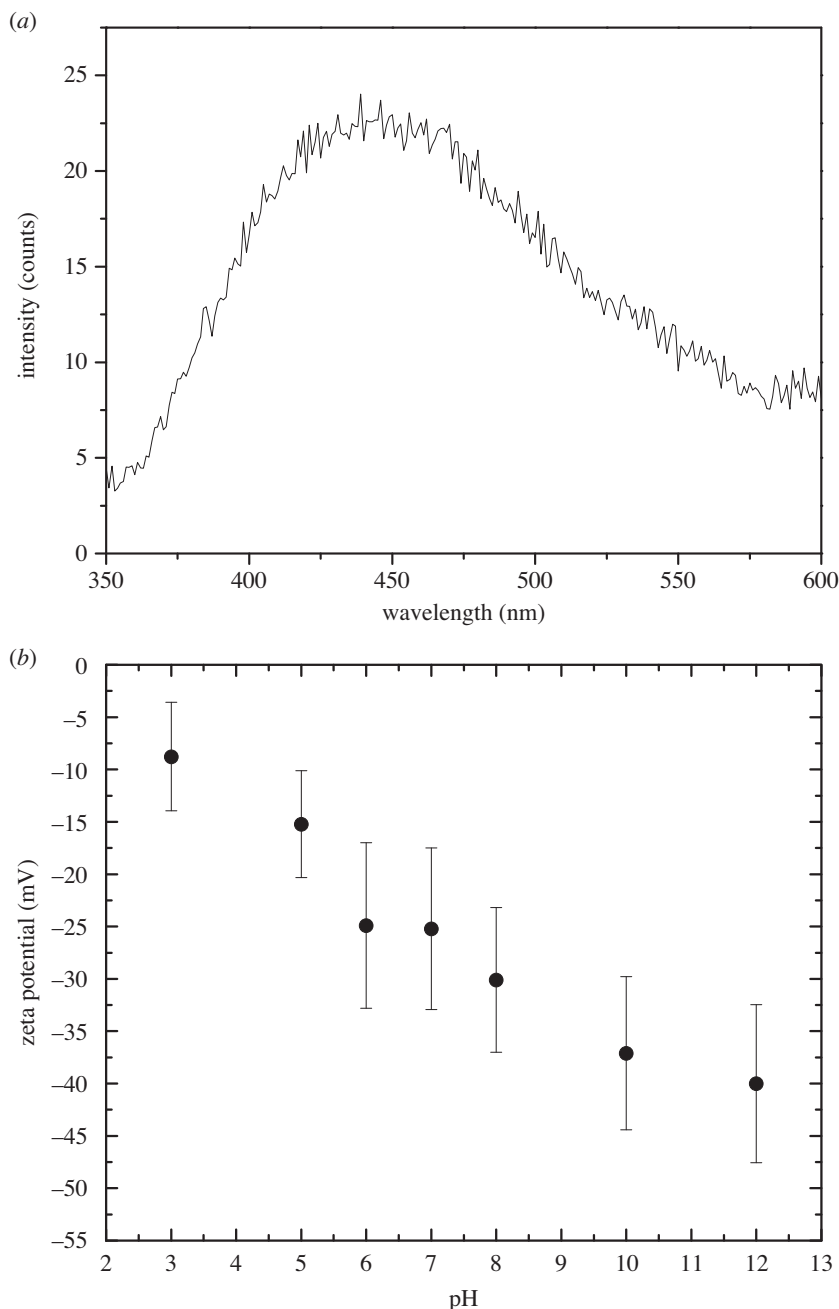


Figure 5. Photoluminescence spectrum measured with 270 nm excitation wavelength (a) and zeta potential (b) determined for Fe_2TiO_5 nanoparticles.

Fe_2TiO_5 [34,35], though many authors have experimentally and by DFT calculations obtained higher values for the indirect band gap in the range 2–2.2 eV [24,27,36–38]. Considering these results, as synthesized Fe_2TiO_5 nanoparticles could have the potential for the degradation of different pollutants in the visible-light region.

3.5. Photoluminescence and colloidal properties

Photoluminescence spectrum of Fe_2TiO_5 nanoparticle powder measured with an excitation wavelength of 270 nm is shown in figure 5a. Overall low values were obtained indicating that recombination of the photo-generated electron-hole pairs is inhibited. The separation efficiency of photo-excited electron-hole pairs is enhanced leading to improved photocatalytic properties [39]. This has been observed before for $\text{Fe}_2\text{TiO}_5/\text{TiO}_2$ nanoheterostructures and composites [39,40].

Determining the point of zero charge (pH_{PZC}) is significant to predict the charge on the nanoparticle surface during photocatalytic degradation of pollutants [41]. The stability of as-synthesized Fe_2TiO_5 particles was analysed by measuring the zeta potential in an aqueous system using a deionized water suspension at room temperature. When metal oxide nanoparticles are dispersed in water or an organic solvent, $-\text{OH}$ surface groups can be protonated or deprotonated leading to surface charged groups ($-\text{OH}_2^+$ or $-\text{O}^-$), respectively. The zeta potential observed for Fe_2TiO_5 particles was -21.6 ± 6.8 mV. This value is negative and high and indicates particle stability in water and low agglomeration [42]. Adsorption of cationic dyes such as MB on a negative surface charge is favoured due to electrostatic forces of attraction (Van der Waals) [43]. Variation of the zeta potential with pH is given in figure 5b. All values were negative showing that the point of zero charge (P_{ZC}) or isoelectric point (IEP) of pseudobrookite is below pH 3. The zeta potential value can be an indicator of the particle surface charge and is influenced by the preparation process [44]. Muthukumar *et al.* [44] obtained high positive values for pseudobrookite (iron titanate) synthesized using a solvothermal method that depended on the duration of treatment in reduced oxygen conditions (19.4 for 5 h, 19.98 for 10 h, 33.6 for 15 h and 17.43 for 20 h). Such values enabled acidic site availability. In our case, the obtained gel was calcined in an air atmosphere rich in oxygen that resulted in a negative charge. Mehdilo *et al.* [45] measured the zeta potential of ilmenite ore (raw, heat-treated (fired) at 500, 600, 750 and 950°C). Compared with raw ilmenite with a point of zero charge (P_{ZC}) determined at pH 5.4, heat treating of ilmenite at 600°C accompanied with the decomposition of ilmenite to haematite and rutile (at 750°C) and then ferric pseudobrookite (Fe_2TiO_5), haematite and rutile at 950°C lead to an overall decrease in zeta potential values over the pH range from 2.5 to 7.5 and shift of the P_{ZC} to pH 3.9, 2.9 and 3 at 600, 750 and 950°C, respectively. Suttiponparmit *et al.* [46] investigated the role of surface area, primary particle size and crystal phase on TiO_2 dispersion properties and determined that in the case of anatase, increase in particle size leads to a reduction of the dispersion zeta potential and increase in hydrodynamic size, with a completely negative zeta potential for particles of 102 nm. This could also be the case for Fe_2TiO_5 and needs further investigation on different-sized particles.

The hydrodynamic radius of Fe_2TiO_5 particles was determined as 175 ± 7 nm. Taking into account that the average particle size was estimated to be around 50 nm in FESEM images and that agglomerates were noted in TEM images, this value shows that some particle aggregation remained.

3.6. Photodegradation of methylene blue

The photocatalytic activity of Fe_2TiO_5 was evaluated by the degradation of MB aqueous solution under direct sunlight.

3.6.1. Effect of initial photocatalyst concentration on methylene blue degradation

The effect of initial photocatalyst concentration under direct sunlight irradiation was investigated by varying the initial Fe_2TiO_5 concentration from 10 to 50 mg per 100 ml of 10 mg l^{-1} MB dye solution as shown in figure 6a. It can be seen from figure 6b that the dye removal efficiency without Fe_2TiO_5 was negligible which is consistent with previously reported literature data [47]. When the amount of photocatalyst was increased from 10 to 50 mg, the photocatalytic activity was found to be increasing, which could be caused by an increased number of active sites on the catalyst surface. Further increase in the catalyst amount above 50 mg decreased the activity, which could be due to the phenomenon of light scattering and screening effects (electronic supplementary material, S.1). Namely, this can be ascribed to the increased aggregation of particles acting as barriers for the light irradiation [48,49].

3.6.2. Effect of the initial dye concentration

The effect of the initial concentration of MB on the decomposition of the dye was investigated by varying the initial concentration from 10 to 30 mg l^{-1} with constant catalyst loading (50 mg). As shown in electronic supplementary material S.2, the photodegradation process decreased with the increase in dye concentration. This can be explained as follows: due to increased adsorption of dye molecules on surface-active sites on the photocatalyst, adsorption of OH^- is decreased, and therefore the formation of the highly oxidative, OH^\bullet radical is reduced. In addition, higher dye concentrations reduce the light path length of the photons thus the light-triggered catalyst decreases [50,51].


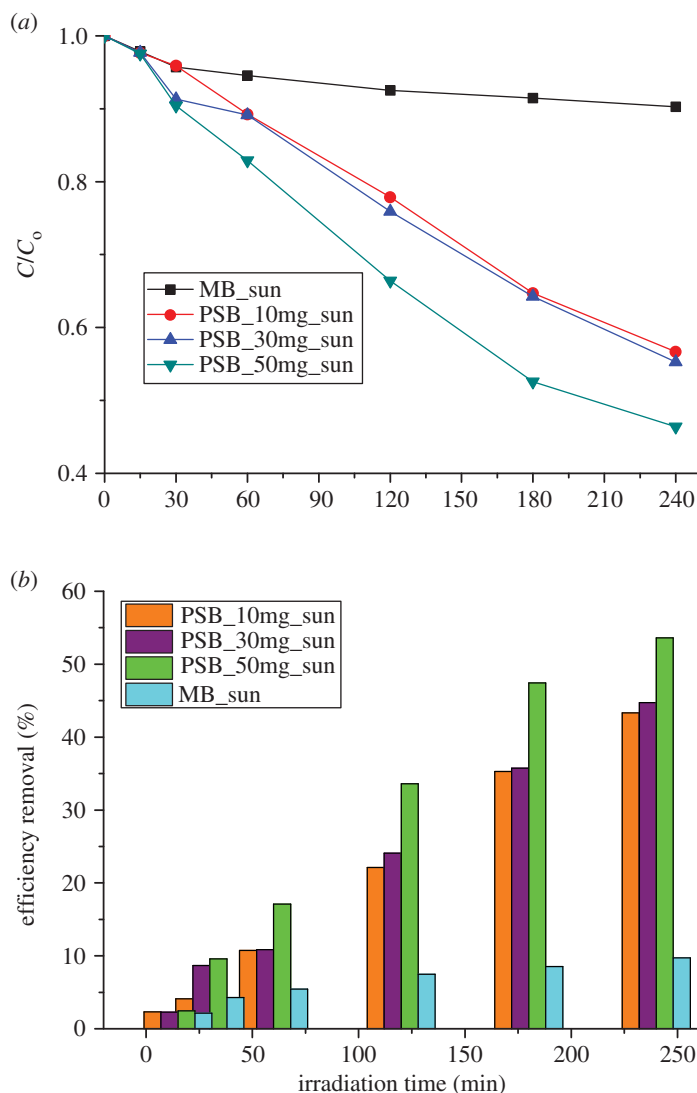



Figure 6. Effect of initial photocatalyst dose on the degradation of MB (a) and percentage removal of MB (b).

3.6.3. Effect of solution pH on the degradation of methylene blue

The pH is considered to be the main parameter in the photocatalytic process, due to its impact on the surface charge of the photocatalyst affecting dye degradation [52]. Hence, an attempt was made to study the influence of pH on the degradation of MB at pH values in the range of 7–11 (figure 7a), and it was adjusted before adsorption. We also investigated photocatalytic degradation in acidic conditions (pH=3), where the influence was negligible. The degradation efficiency increased with increased pH (97% at pH=11) which is 1.79 times higher than the degradation efficiency at the normal pH condition. The corresponding colour change is given in electronic supplementary material, S.3. Since the zeta potential was negative with pH change, it is expected that adsorption of MB (cationic dye) on the surface of the Fe_2TiO_5 photocatalyst would be enhanced at higher pH values [1,53]. Namely, in the photocatalytic oxidation process after irradiation and excitation of electrons from the valence to the conduction band (figure 8), photo-generated holes either directly oxidize dye to reactive intermediates (equation (3.2)) or react with hydroxyl ions (OH^-) leading to the formation of highly oxidative hydroxyl radicals ($\text{OH}\cdot$) and further complete mineralization of the dye (equation (3.5)) [54].



and



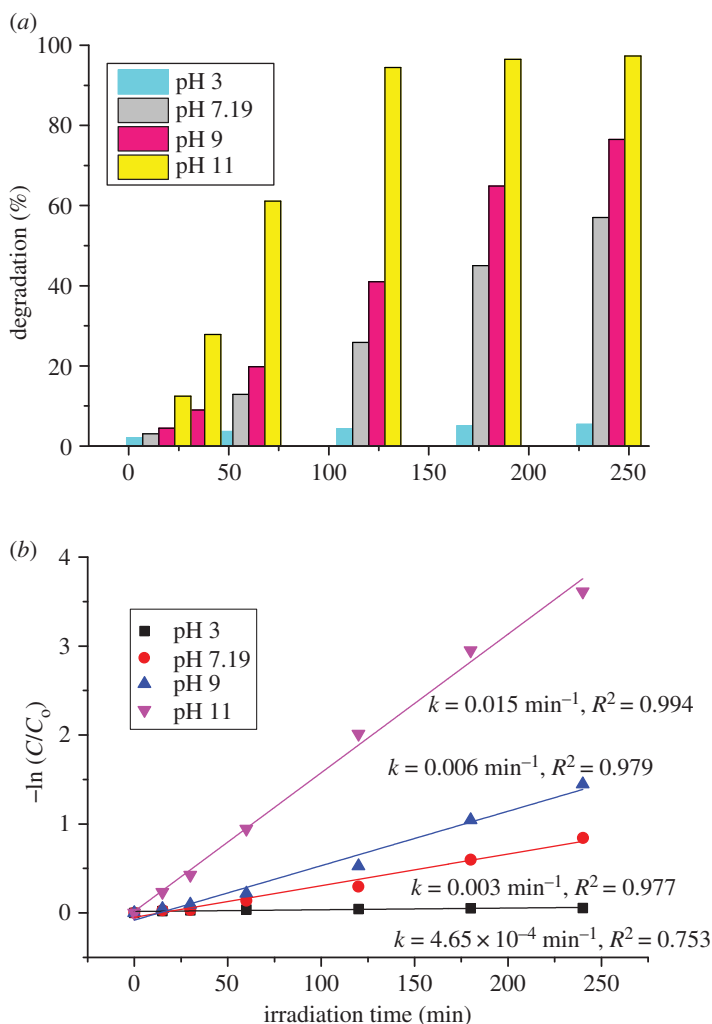


Figure 7. Efficiency of removal of MB—effect of the initial pH on the degradation of MB (a) and pseudo-first-order kinetics curves of the degradation of MB under sunlight in the presence of Fe_2TiO_5 with different initial pH values (b). Experimental conditions: Fe_2TiO_5 , 50 mg l^{-1} and MB 10 mg l^{-1} .

or



and



However, since the adsorption of dye was low as the surface area was moderate ($11.8 \text{ m}^2 \text{ g}^{-1}$), a possible reason for enhanced photocatalytic degradation of MB at higher pH values is the formation of OH radicals due to a large number of hydroxyl ions in the alkaline medium [55].

A simplified Langmuir–Hinshelwood (L–H) kinetic model (equation 3.5) was used to describe the photocatalytic degradation rate of MB by plotting the graph of $-\ln(C/C_0)$ versus time, t , (figure 7b) at different pH values [49].

$$-\ln \frac{C}{C_0} = kt, \quad (3.5)$$

where C_0 and C are the concentrations of MB in solution at time 0 and t , respectively, and k is the apparent first-order reaction rate constant. The obtained values of k are equal to 4.65×10^{-4} , 0.00356, 0.00612 and 0.016 min^{-1} for initial pH values 3, 7.19, 9 and 11, while correlation constants, R^2 , for the fitted lines were 0.753, 0.977, 0.979 and 0.994, respectively.

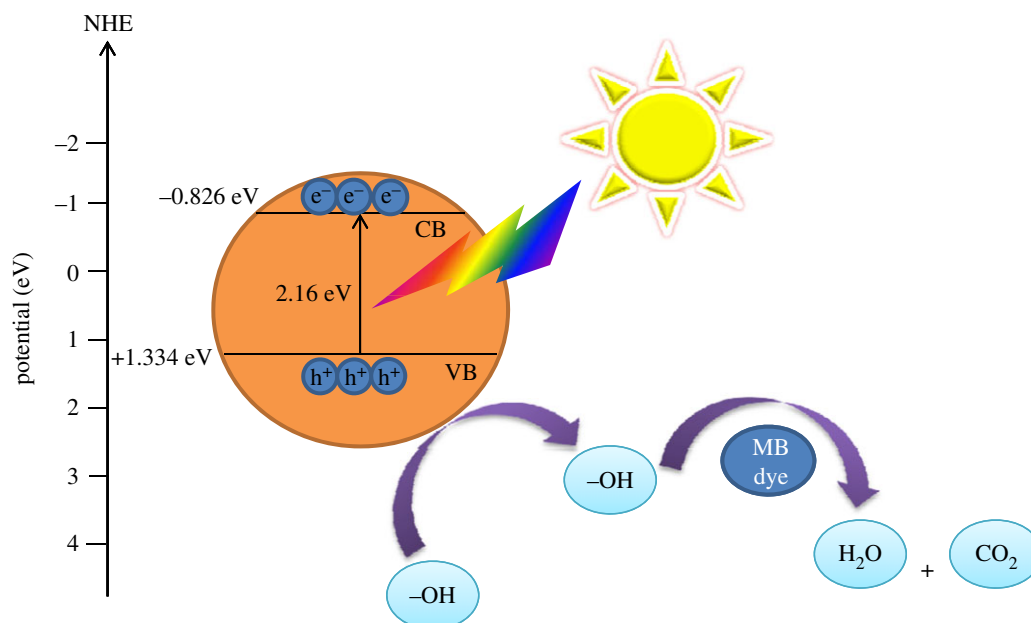


Figure 8. Scheme of the band gap structure of Fe_2TiO_5 and the possible mechanism for the photocatalytic degradation of MB dye over Fe_2TiO_5 photocatalyst.

3.6.4. Possible mechanism of methylene blue degradation

Efficient charge separation is the key factor determining the photocatalytic activity of a semiconducting photocatalyst. Thus, it was essential to determine the conduction band (CB) and valence band (VB) potentials of the Fe_2TiO_5 photocatalyst, using the following empirical equations [56]:

$$E_{VB} = \chi + 0.5E_g - E^e \quad (3.6)$$

and

$$E_{CB} = E_{VB} - E_g, \quad (3.7)$$

where E_{VB} is the valence band (VB) edge potential, E_{CB} is the conduction band (CB) edge potential, χ is the electronegativity of the semiconductor, E^e is the energy of free electrons on the hydrogen scale (4.5 eV) and E_g is the band gap energy of the semiconductor. Electronegativity of Fe_2TiO_5 was calculated using the following equation:

$$\chi = [\chi(A)^a \chi(B)^b \chi(C)^c]^{1/a+b+c}, \quad (3.8)$$

where a , b and c are the number of atoms in the compound, while electronegativity of Fe, Ti and O was calculated as the arithmetic mean of the atomic electron affinity and the first ionization energy [57]. The value of χ of Fe_2TiO_5 was calculated to be 2.086 while E_{CB} and E_{VB} were estimated to be -0.826 and $+1.334$ eV versus normal hydrogen electrode (NHE) and results are presented in figure 8. The conduction band of Fe_2TiO_5 is more negative than that of $\text{O}_2/\cdot\text{O}_2^-$ (-0.282 eV versus NHE); therefore, the electrons can reduce O_2 to generate superoxide anions $\cdot\text{O}_2^-$, while the E_{VB} of Fe_2TiO_5 ($+1.334$ eV versus NHE) was not positive enough to oxidize $\text{OH}^-/\text{H}_2\text{O}$ (2.27 V versus NHE) to form active species $\cdot\text{OH}$ [58]. This indicates that MB dye was degraded mainly by the active species $\cdot\text{O}_2^-$ and by the accumulation of holes. Enhanced photocatalytic degradation efficiency could be ascribed to a large number of hydroxyl ions in the alkaline medium, as mentioned above.

4. Conclusion

In summary, Fe_2TiO_5 nanopowder was successfully synthesized through a simple sol-gel route followed by calcination at 750°C . The Fe_2TiO_5 powder consisted of relatively uniformly sized nanoparticles with a rhombic shape and an average diameter of around 50 nm. The specific surface area from BET analysis was around $11.8 \text{ m}^2 \text{ g}^{-1}$. The band gap was estimated to be 2.16 eV. The zeta potential observed for Fe_2TiO_5 was negative and high and indicated particle stability in water and low agglomeration.

Photocatalytic measurements showed that as-synthesized Fe_2TiO_5 displays moderate degradation efficiency. The degradation of efficiency significantly depends on the particle specific surface area. In addition, catalyst loading and pH of the solution greatly affected the degradation process. A reaction mechanism was proposed.

Data accessibility. Material characterization results and methylene blue aqueous solution degradation data are available at the Dryad Digital Repository (<https://doi.org/10.5061/dryad.69p8cz8z5>) [59]. Additional information concerning this paper is available in the electronic supplementary material

Authors' contributions. Z.Z.V. conceived and designed the study, synthesized the powder, performed photocatalytic experiments and spectroscopic analysis, and drafted the manuscript. M.P.D. participated in the laboratory work, especially photocatalytic experiments and spectroscopic analysis, and critically revised the manuscript. J.D.V. measured and analysed FESEM images. I.J.-C. performed measurement of nitrogen adsorption/desorption isotherms and analysed obtained data. M.O. measured and analysed the zeta potential and particle size. N.B.T. measured X-ray diffraction spectra. S.S. measured and analysed photoluminescence spectra. G.O.B. measured and analysed TEM images. M.V.N. helped conceive and design the study, coordinated the study, analysed XRD data and TEM images, measured and analysed FTIR spectra and helped draft the manuscript. All authors gave final approval for publication and agree to be held accountable for the work performed therein.

Competing interests. We declare we have no competing interests.

Funding. This work was funded by the Ministry for Education, Science and Technological Development of the Republic of Serbia with contracts for realization and financing scientific research with the Institute of Technical Sciences of SASA no. 451-03-68/2020-14/200175 (Z.Z.V. and J.D.V.) and with the Institute for Multidisciplinary Research, University of Belgrade, no. 451-03-68/2020-14/200053 (M.P.D., G.O.B. and M.V.N.)

Acknowledgements. The support of the bilateral cooperation with Slovenia is also gratefully acknowledged (project no. BI-RS-18-19-026). The TEM work was conducted in the Centre for Electron Microscopy and Microanalysis (CEMM) at Jožef Stefan Institute, Ljubljana (Slovenia).

References

- Liu Y, Yu H, Lv Z, Zhan S, Yang J, Peng X, Ren Y, Wu X. 2012 Simulated-sunlight-activated photocatalysis of Methylene Blue using cerium-doped $\text{SiO}_2/\text{TiO}_2$ nanostructured fibers. *J. Environ. Sci.* **24**, 1867–1875. (doi:10.1016/S1001-0742(11)61008-5)
- Aksu Z. 2005 Application of biosorption for the removal of organic pollutants: a review. *Process Biochem.* **40**, 997–1026. (doi:10.1016/j.procbio.2004.04.008)
- Appavu B, Thirupuranthagan S, Ranganathan S, Erusappan E, Kannan K. 2018 $\text{BiVO}_4/\text{N-rGO}$ nano composites as highly efficient visible active photocatalyst for the degradation of dyes and antibiotics in eco system. *Ecotoxicol. Environ. Saf.* **151**, 118–126. (doi:10.1016/j.ecoenv.2018.01.008)
- Brillas E, Martínez-Huitle CA. 2015 Decontamination of wastewaters containing synthetic organic dyes by electrochemical methods: an updated review. *Appl. Catal. B* **166–167**, 603–643. (doi:10.1016/j.apcatb.2014.11.016)
- Chan S, Wu TY, Juan JC, Teh CY. 2011 Recent developments of metal oxide semiconductors as photocatalysts in advanced oxidation processes (AOPs) for treatment of dye waste-water. *J. Chem. Technol. Biotechnol.* **86**, 1130–1158. (doi:10.1002/jctb.2636)
- Cheng M, Zeng G, Huang D, Lai C, Xu P, Zhang C, Liu Y. 2016 Hydroxyl radicals based advanced oxidation processes (AOPs) for remediation of soils contaminated with organic compounds: a review. *Chem. Eng. J.* **284**, 582–598. (doi:10.1016/j.cej.2015.09.001)
- Debabrata C, Shimanti D. 2005 Visible light induced photocatalytic degradation of organic pollutants. *J. Photochem. Photobiol. C* **6**, 186–205. (doi:10.1016/j.jphotochemrev.2005.09.001)
- Hoffmann MR, Martin ST, Choi W, Bahnemann DW. 1995 Environmental applications of semiconductor photocatalysis. *Chem. Rev.* **95**, 69–96. (doi:10.1021/cr00033a004)
- Park H, Park Y, Kim W, Choi W. 2013 Surface modification of TiO_2 photocatalyst for environmental applications. *J. Photochem. Photobiol. C* **15**, 1–20. (doi:10.1016/j.jphotochemrev.2012.10.001)
- Mishra M, Doo-Man C. 2015 $\alpha\text{-Fe}_2\text{O}_3$ as a photocatalytic material: a review. *Appl. Catal. A* **498**, 126–141. (doi:10.1016/j.apcata.2015.03.023)
- Mulmudi HK, Mathews N, Dou XC, Xi LF, Pramana SS, Lam YM, Mhaisalkar SG. 2011 Controlled growth of hematite ($\alpha\text{-Fe}_2\text{O}_3$) nanorod array on fluorine doped tin oxide: synthesis and photoelectrochemical properties. *Electrochem. Commun.* **13**, 951–954. (doi:10.1016/j.elecom.2011.06.008)
- Moradlou O, Rabiei Z, Banazadeh A, Warzywoda J, Zirak M. 2018 Carbon quantum dots as nano-scaffolds for $\alpha\text{-Fe}_2\text{O}_3$ growth: preparation of $\text{Ti}/\text{CQD}@\alpha\text{-Fe}_2\text{O}_3$ photoanode for water splitting under visible light irradiation. *Appl. Catal. B Environ.* **227**, 178–189. (doi:10.1016/j.apcatb.2018.01.016)
- Liu Q *et al.* 2014 Aligned Fe_2TiO_5 -containing nanotube arrays with low onset potential for visible-light water oxidation. *Nat. Commun.* **5**, 5122. (doi:10.1038/ncomms6122)
- Deng J *et al.* 2015 Thin-layer Fe_2TiO_5 on hematite for efficient solar water oxidation. *ACS Nano* **9**, 5348–5356. (doi:10.1021/acsnano.5b01028)
- Agafonov AV, Afanasyev DA, Gerasimova TV, Krayev AS, Kashirin MA, Vinogradov VV, Vinogradov AV, Kessler VG. 2016 Nanoparticle self-assembly mechanisms in the colloidal synthesis of iron titanate nanocomposite photocatalysts for environmental applications. *ACS Sustain. Chem. Eng.* **4**, 2814–2821. (doi:10.1021/acssuschemeng.6b00317)
- Ramezani M, Davoodi A, Malekizad A, Mostafa Hosseiniour-Mashkani S. 2015 Synthesis and characterization of Fe_2TiO_5 nanoparticles through a sol-gel method and its photocatalyst applications. *J. Mater. Sci. Mater. Electron.* **26**, 3957–3962. (doi:10.1007/s10854-015-2930-6)
- Momma K, Izumi F. 2011 VESTA 3 for three dimensional visualization of crystal, volumetric and morphology data. *J. Appl. Crystallogr.* **44**, 1271–1276. (doi:10.1107/S0021889811038970)
- Toby BH, Von Dreele RB. 2013 GSAS II the genesis of an open-source all-purpose crystallography software package. *J. Appl. Crystallogr.* **46**, 544–549. (doi:10.1107/S0021889813003531)
- Petit S *et al.* 2016 How should iron and titanium be combined in oxides to improve photoelectrochemical properties? *J. Phys. Chem.* **120**, 24 521–24 532. (doi:10.1021/acs.jpcc.6b05794)
- Nikolic MV, Vasiljevic ZZ, Lukovic MD, Pavlovic VJ, Vujancevic J, Radovanovic M, Krstic JB, Vlahovic B, Pavlovic VB. 2018 Humidity sensing properties of nanocrystalline pseudobrookite (Fe_2TiO_5) based thick films. *Sens. Actuators B*

- Chem.* **277**, 654–664. (doi:10.1016/j.snb.2018.09.063)
21. Kumar L, Kar M. 2011 Influence of Al³⁺ ion concentration on the crystal structure and magnetic anisotropy of nanocrystalline spinel cobalt ferrite. *J. Magn. Magn. Mater.* **323**, 20 142–22 048.
 22. Guo WQ, Malus S, Ryan DH, Altounian Z. 1999 Crystal structure and cation distributions in the Fe_{1-x}O₃-Fe₂TiO₅ solution series. *J. Phys.: Condens. Matter.* **11**, 6337–6346. (doi:10.1088/0953-8984/11/33/304)
 23. Rodrigues JEFs *et al.* 2019 Spin-phonon coupling in uniaxial anisotropic spin-glass based on Fe₂TiO₅ pseudobrookite. *J. Alloys Compd.* **799**, 563–572. (doi:10.1016/j.jallcom.2019.05.343)
 24. Pal B, Sharon M, Nogami G. 1999 Preparation and characterization of TiO₂/Fe₂O₃ binary mixed oxides and its photocatalytic properties. *Mater. Chem. Phys.* **59**, 254–261. (doi:10.1016/S0254-0584(99)00071-1)
 25. Salarazadeh P, Javanbakht M, Pourmahdian S, Bagheri A, Beydaghi H, Enhessari M. 2016 Surface modification of Fe₂TiO₅ nanoparticles by silane coupling agent: synthesis and application in proton exchange composite membranes. *J. Colloid Interface Sci.* **472**, 135–144. (doi:10.1016/j.jcis.2016.03.036)
 26. Li S, Zhong J, Cui Z, Zhang Q, Sun M, Wang Y. 2019 Electron beam-induced morphology transformations of Fe₂TiO₅ nanoparticles. *J. Mater. Chem. C* **7**, 13 829–13 838. (doi:10.1039/C9TC04561A)
 27. Karimi B, Habibi MH. 2019 High photocatalytic activity of light-driven Fe₂TiO₅ nanoheterostructure toward degradation of antibiotic metronidazole. *J. Ind. Eng. Chem.* **80**, 292–300. (doi:10.1016/j.jiec.2019.08.007)
 28. Hanaor DAH, Sorrell CC. 2011 Review of anatase to rutile phase transformation. *J. Mater. Sci.* **46**, 855–874. (doi:10.1007/s10853-010-5113-0)
 29. Giesen B, Orthner HR, Kowalik A, Roth P. 2004 On the interaction of coagulation and coalescence during gas-phase synthesis of Fe-nanoparticle agglomerates. *Chem. Eng. Sci.* **59**, 2201–2221. (doi:10.1016/j.ces.2004.02.013)
 30. Thommes M, Kaneko K, Neimark AV, Olivier JP, Rodriguez-Reinoso F, Rouquerol J, Sing KSW. 2015 Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report). *Pure Appl. Chem.* **87**, 1051–1069. (doi:10.1515/pac-2014-1117)
 31. Zhao XS, Lu GQ, Millar GJ. 1996 Advances in mesoporous molecular sieve MCM-41. *Ind. Eng. Chem. Res.* **35**, 2075–2090. (doi:10.1021/ie950702a)
 32. Tauc J, Mentha A, Wood DL. 1970 Optical and magnetic investigations of the localized states in semiconducting glasses. *Phys. Rev. Lett.* **25**, 749–752. (doi:10.1103/PhysRevLett.25.749)
 33. Davis EA, Mott NF. 1970 Conduction in non-crystalline systems V. Conductivity, optical absorption and photoconductivity in amorphous semiconductors. *Phil. Mag.* **22**, 903–922. (doi:10.1080/14786437008221061)
 34. Vasiljevic ZZ, Lukovic MD, Nikolic MV, Tasic NB, Mitric M, Aleksic OS. 2015 Nanostructured Fe₂O₃/TiO₂ thick films: analysis of structural and electronic properties. *Ceram. Int.* **41**, 6889–6897. (doi:10.1016/j.ceramint.2015.01.141)
 35. Kozuka H, Kajimira M. 2001 Sol-gel preparation and photoelectrochemical properties of Fe₂TiO₅ thin films. *J. Sol. Gel. Sci. Technol.* **22**, 125–132. (doi:10.1023/A:1011228706934)
 36. Courtin E, Baldinozzi G, Sougrati MT, Stievano L, Sanchez C, Laberty-Robert C. 2014 New Fe₂TiO₅-based nanoheterostructured mesoporous anodes with improved visible light photoresponses. *J. Mater. Chem. A* **2**, 6567–6577. (doi:10.1039/C4TA00102H)
 37. Bassi PS, Chiam SY, Barber J, Wong LH. 2014 Hydrothermal grown nanoporous iron based titanate, Fe₂TiO₅ for light driven water splitting. *ACS Appl. Mat. Interfaces* **6**, 22 490–22 495. (doi:10.1021/am5065574)
 38. Ngo HD *et al.* 2019 Structure and optical properties of sputter deposited pseudobrookite thin films. *Cryst. Eng. Com.* **21**, 34–40. (doi:10.1039/C8CE01475B)
 39. Lou Z, Li Y, Song H, Ye Z, Zhu L. 2016 Fabrication of Fe₂TiO₅/TiO₂ nanoheterostructures with enhanced visible-light photocatalytic activity. *RSC Adv.* **6**, 45 343–45 348. (doi:10.1039/C6RA06763H)
 40. Aleksic OS, Vasiljevic ZZ, Vujkovic M, Nikolic M, Labus N, Lukovic MD, Nikolic MV. 2017 Structural and electronic properties of Fe₂O₃/TiO₂ thick films and their photoelectrochemical behaviour. *J. Mater. Sci.* **52**, 5938–5953. (doi:10.1007/s10853-017-0830-2)
 41. Azeez F, Al-Hetlani E, Arafat M, Abdelmonem Y, Abdel Nazeer A, Amin MO, Madkour M. 2018 The effect of surface charge on photocatalytic degradation of methylene blue dye using chargeable titania nanoparticles. *Sci. Rep.* **8**, 7104. (doi:10.1038/s41598-018-25673-5)
 42. Nidhin M, Indumathy R, Sreeman KJ, Nair BJ. 2008 Synthesis of iron oxide nanoparticles of narrow size distribution on polysaccharide templates. *Bull. Mater. Sci.* **31**, 93–96. (doi:10.1007/s12034-008-0016-2)
 43. Abhilash MR, Akshatha G, Srikantaswamy S. 2019 Photocatalytic dye degradation and biological activities of the Fe₂O₃/Cu₂O nanocomposite. *RSC Adv.* **9**, 8557–8568. (doi:10.1039/C8RA09929D)
 44. Muthukumar K, Lakshmi DS, Gujar RB, Boricha AB, Mohapatra PK, Bajaj HC. 2016 Synthesis and characterization of magnetic copper-iron-titanate and uptake studies of americium from nuclear waste solutions. *RSC Adv.* **6**, 111 822–111 830. (doi:10.1039/C6RA24266A)
 45. Mehdilo A, Irannajad M, Rezaei B. 2013 Effect of oxidation roasting on ilmenite flotation. *Physicochem. Probl. Miner. Process.* **50**, 493–505. (doi:10.5277/ppmp140206)
 46. Suttiponpanit K, Jiang J, Sahu M, Suvachittanon S, Charinpanitkul T, Biswas P. 2011 Role of surface area, primary particle size and crystal phase on titanium dioxide nanoparticle dispersion properties. *Nanoscale Res. Lett.* **6**, 27. (doi:10.1007/s11671- 9772-1)
 47. Soltani T, Entezari MH. 2013 Photolysis and photocatalysis of methylene blue by ferrite bismuth nanoparticles under sunlight irradiation. *J. Mol. Catal. A Chem.* **377**, 197–203. (doi:10.1016/j.molcata.2013.05.004)
 48. Zhang YX, Hao XD, Li F, Diao ZP, Guo ZY, Li J. 2014 pH-dependent degradation of methylene blue via rational-designed MnO₂ nanosheet-decorated diatomites. *Ind. Eng. Chem. Res.* **53**, 6966–6977. (doi:10.1021/ie5002229)
 49. Paul DR, Sharma R, Nehra SP, Sharma A. 2019 Effect of calcination temperature, pH and catalyst loading on photodegradation efficiency of urea derived graphitic carbon nitride towards methylene blue dye solution. *RSC Adv.* **9**, 15381. (doi:10.1039/C9RA02201E)
 50. Akyol A, Yatmaz HC, Bayramoglu M. 2004 Photocatalytic decolorization of Remazol Red RR in aqueous ZnO suspensions. *Appl. Catal. B: Environ.* **54**, 19–24. (doi:10.1016/j.apcatb.2004.05.021)
 51. Liu CC, Hsieh YH, Lai PF, Li CH, Kao CL. 2006 Photodegradation treatment of azo dye wastewater by UV/TiO₂ process. *Dyes Pigm.* **68**, 191–195. (doi:10.1016/j.dyepig.2004.12.002)
 52. Abdellah MH, Nosier SA, El-Shazli AH, Mubarak AA. 2018 Photocatalytic decolorization of methylene blue using TiO₂/UV system enhanced by air sparging. *Alex. Eng. J.* **57**, 3727–3735. (doi:10.1016/j.aej.2018.07.018)
 53. Jing HP, Wang CC, Zhang YW, Wang P, Li R. 2014 Photocatalytic degradation of methylene blue in ZIF-8. *RSC Adv.* **4**, 54454. (doi:10.1039/C4RA08820D)
 54. Kansal SK, Kaur N, Singh S. 2009 Photocatalytic degradation of two commercial reactive dyes in aqueous phase using nanophotocatalysts. *Nanoscale Res. Lett.* **4**, 709. (doi:10.1007/s11671-009-9300-3)
 55. Wang CC, Lee CK, Lyu MD, Juang LC. 2008 Photocatalytic degradation of C.I. Basic Violet 10 using TiO₂ catalysts supported by Y zeolite: an investigation of the effects of operational parameters. *Dyes Pigm.* **76**, 817–824. (doi:10.1016/j.dyepig.2007.02.004)
 56. Kim Y, Atherton SJ, Brigham ES, Mallouk TE. 1993 Sensitized layered metal oxide semiconductor particles for photochemical hydrogen evolution from nonsacrificial electron donors. *J. Phys. Chem.* **97**, 11 802–11 810. (doi:10.1021/j100147a038)
 57. Nethercot AH. 1974 Prediction of fermi energies and photoelectric thresholds based on electronegativity concepts. *Phys. Rev. Lett.* **33**, 1088–1091. (doi:10.1103/PhysRevLett.33.1088)
 58. Fujishima A, Zhang X. 2006 Titanium dioxide photocatalysis: present situation and future approaches. *C. R. Chim.* **9**, 750–760. (doi:10.1016/j.crci.2005.02.055)
 59. Vasiljevic ZZ, Dojcinovic MP, Vujanecic JD, Jankovic-Castvan I, Ognjanovic M, Tadic NB, Stojadinovic S, Brankovic GO, Nikolic MV. 2020 Data from: Photocatalytic degradation of methylene blue under natural sunlight using Fe₂TiO₅ nanoparticles prepared by modified sol-gel method. Dryad Digital Repository. (doi:10.5061/dryad.69p8cz825)