



Serbian | Српско  
Microscopy | Друштво за  
Society | Микроскопију

# MCM2019

PROCEEDINGS

from the

## **14<sup>th</sup> MULTINATIONAL CONGRESS ON MICROSCOPY**

September 15–20, 2019, Belgrade, Serbia

PROCEEDINGS  
from the  
**14<sup>th</sup> MULTINATIONAL  
CONGRESS  
ON MICROSCOPY**

SEPTEMBER 15–20, 2019, BELGRADE, SERBIA

**MCM2019**  
**14<sup>th</sup> MULTINATIONAL CONGRESS ON MICROSCOPY**  
**SEPTEMBER 15–20, 2019 IN BELGRADE, SERBIA**

**TITLE:**

Proceedings from the 14<sup>th</sup> Multinational Congress on Microscopy, September 15–20, 2019, Belgrade, Serbia

**PUBLISHERS:**

University of Belgrade, Institute for Biological  
Research "Siniša Stanković", National Institute of Republic of Serbia  
Serbian Society for Microscopy, Serbia

**FOR PUBLISHERS:**

Dr. Mirjana Mihailović  
Dr. Jasmina Grbović Novaković

**EDITORS:**

Dr. Jasmina Grbović Novaković  
Dr. Nataša Nestorović  
Dr. Dragan Rajnović

ISBN 978-86-80335-11-7

**PRINT:**

Knjigoveznica i kartonaža Grbović M. Milica, M. Gorkog 43, Beograd 11000, Serbia  
30 e-copies

Copyright © 2019

by Institute for Biological Research "Siniša Stanković" and others contributors.

All rights reserved. No part of this publication may be reproduced, in any form or by any means,  
without permission in writing from the publisher

## COMMITTEES AND BOARDS

### CHAIRS/LOC

Jasmina Grbovic Novakovic  
Center of Excellence CONVINCE, VINCA Institute of Nuclear Sciences, University of Belgrade,  
Belgrade, Serbia

Natasa Nestorovic  
Institute for Biological Research "Sinisa Stankovic", University of Belgrade, Belgrade, Serbia

Dragan Rajnovic  
Faculty of Technical Sciences, University of Novi Sad, Novi Sad, Serbia

### International Organizing Committee

Gerd Leitinger Medical University of Graz, Graz, Austria	Vladislav Krzyzanek Institute of Scientific Instruments of the Czech Academy of Science, Brno, Czech Republic
Bernardi Johannes Vienna University of Technology, Vienna, Austria	Rok Kostanjsek University of Ljubljana, Ljubljana, Slovenia
Goran Kovacevic University of Zagreb, Zagreb, Croatia	Saso Sturm Jozef Stefan Institute, Ljubljana, Slovenia
Andreja Gajovic Rudjer Boskovic Institute, Zagreb, Croatia	Serap Arbak Acibadem Mehmet Ali Aydinlar University, Istanbul, Turkey
Bela Pecz Institute of Technical Physics and Materials Science of Hungarian Academy of Sciences, Budapest, Hungary	Servet Turan Eskisehir Technical University, Eskisehir, Turkey
Kristof Zoltan Eotvos Lorand University, Budapest, Hungary	Jasmina Grbovic Novakovic VINCA Institute of Nuclear Sciences, University of Belgrade, Belgrade, Serbia
Elisabeta Felcieri University of Urbino Carlo Bo, Urbino, Italy	Natasa Nestorovic Institute for Biological Research "Sinisa Stankovic", University of Belgrade, Belgrade, Serbia
Roberto Balboni CNR Institute for Microelectronics and Microsystems, Bologna, Italy	Dragan Rajnovic, Faculty of Technical Sciences, University of Novi Sad, Novi Sad, Serbia
Dusan Chorvat International Laser Center, Bratislava, Slovak Republic	

# Imaging FTIR microscopy – technique for rapid screening of plant cell walls

JASNA SIMONOVIĆ RADOSAVLJEVIĆ<sup>1</sup>, JASNA STEVANIC<sup>2</sup>, DANIELA ĐIKANOVIĆ<sup>1</sup>,  
ALEKSANDRA LJ. MITROVIĆ<sup>1</sup>, LENNART SALMÉN<sup>2</sup>, KSENIJA RADOTIĆ<sup>1</sup>

<sup>1</sup> University of Belgrade, Institute for multidisciplinary research, Belgrade, Serbia; <sup>2</sup> RISE/ Invenia, Stockholm, Sweden

## 1. Introduction

Plant cell walls (CW) are the most abundant, renewable and biodegradable composite on Earth. Cell wall can also be considered as a nano-composite in which cellulose, lignin and hemicelluloses are interconnected in a specific manner. Biopolymers such as cellulose, hemicellulose and lignin, have wide applications in different industries, especially for biofuels and biomaterials [1,2]. By using imaging FTIR microscopy, run in transmission mode and at different polarisation modes (from 0° to 90°), it is possible to follow chemical variability and orientation of cell wall polymers [3]. The orientation of cellulose, xylan and lignin, as essential components of plants, were analysed by iFTIR with regard to the sample axis.

## 2. Materials and Methods

The purified isolated cell wall material was obtained from maple leaves (*A. platanoides*) by methanol extraction and subsequent purification using a series of solvents (1% Triton X-100, 1M sodium chloride, distilled water, methanol, acetone) [4].

FTIR microscopy measurements were carried out using a Spectrum Spotlight 400 FTIR Imaging System (Perkin Elmer Inc, Shelton, CT, USA). The area of interest was first displayed, using a visible CCD camera to locate the cell wall area, which was then irradiated using mid-IR light (Figure 1). The scanning was carried out in imaging mode using an array detector, providing a pixel resolution of 6.25 μm x 6.25 μm, a spectral resolution of 4 cm<sup>-1</sup> and a spectral range from 1,800 to 720 cm<sup>-1</sup>. IR scanning with a polarisation, where the incident IR radiation is polarised by a gold wire grid polariser, in our case, from 0° to 90° polarisation and in relation to the fibre orientation with intervals of 5° were carried out also. In this way, it is possible to investigate, for example, orientations of different polymers in a wood fibre. The IR spectra were processed by the software Spotlight 1.5.1, HyperView 3.2 and Spectrum 6.2.0 (Perkin Elmer Inc., Shelton, CT, USA) [3].

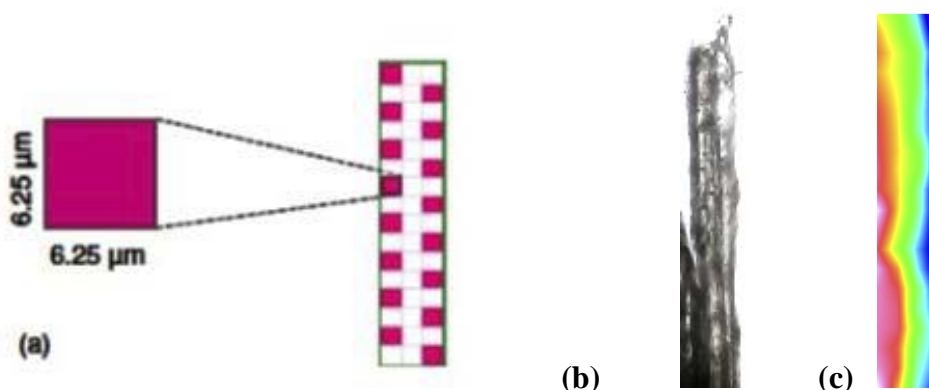


Figure 1. (a) schematic image of the linear array detector containing 16 MCT detectors, also showing one magnified pixel of a 6.25 μm x 6.25 μm, (b) visible image of a part of maple leaves cell wall, (c) IR full-spectral image of the sam part of maple leaves cell wall.

### 3. Results and Discussion

From the in-depth study of polymer orientation, three areas from the sample (maple leaf) were selected. The transmission spectra were recorded from 0° to 90° polarisation modes. Figure 1 shows FTIR spectrum of cell walls of maple leaves in the region 800–1800 cm<sup>-1</sup>. Spectral signals related to absorptions from cellulose, xylan and lignin can be identified.

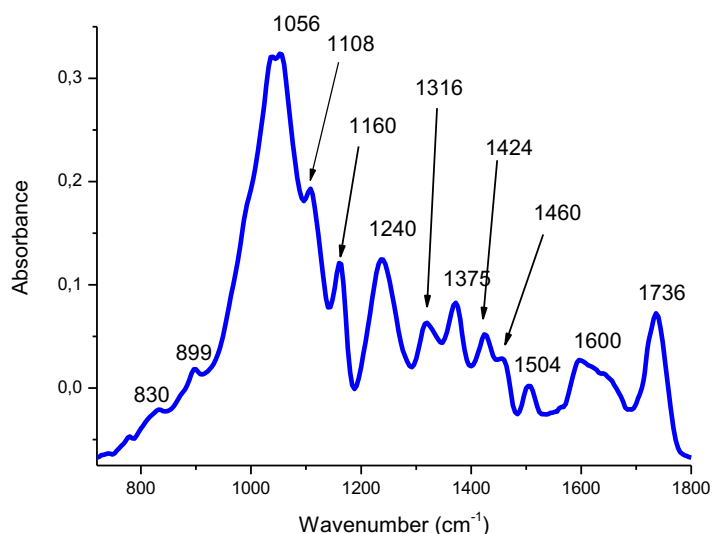


Figure 2. Average absorbance spectrum of maple leaves cell wall.

The relative absorbance spectra are presented (Figure 2) as specific absorption peaks ( $RA = (I_p - I_{min}) / (I_{max} - I_{min})$ ) where RA is relative absorbance,  $I_p$  is intensity of the absorbed IR radiation at a given angle of the polarisation,  $I_{max}$  is maximal intensity observed for a given vibration and  $I_{min}$  is minimal intensity observed for a given vibration. These relative absorbance values were presented in relation to the angle of the incident IR polarisation (from 0° to 90°).

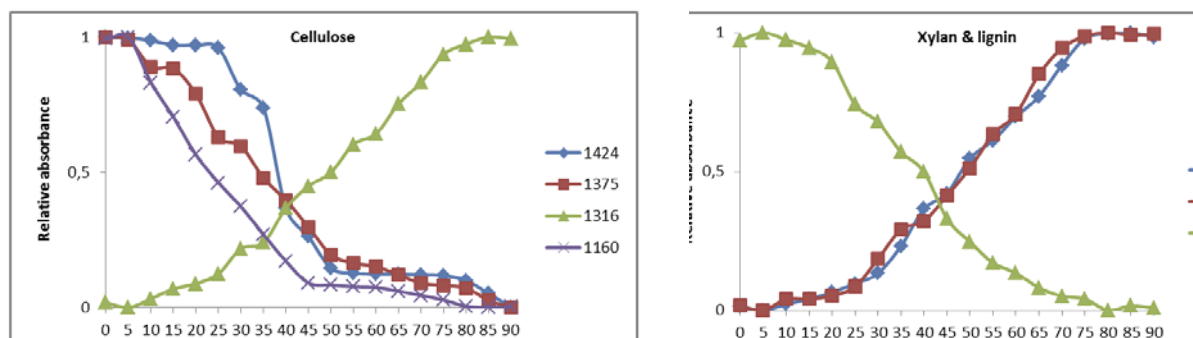


Figure 3. The relative absorbance of IR specific absorption wavenumbers plotted against the polarisation angle for the different polymers (cellulose - left, xylan & lignin – right) for maple leaves.

It is evident (Figure 3 left) that the three cellulose peaks ( $1160\text{ cm}^{-1}$ ,  $1375\text{ cm}^{-1}$  and  $1424\text{ cm}^{-1}$ ) [3–5] had high absorption levels at low polarisation angles, which is a consequence of a more parallel orientation of the corresponding groups to the CW longitudinal axis. The fourth cellulose peak (the perpendicular signal at  $1316\text{ cm}^{-1}$ ) had the greatest intensity at a high polarisation angle, due to the perpendicular orientation of the corresponding group (Figure 3 left). For the xylan, the characteristic band signals ( $1244\text{ cm}^{-1}$ ,  $1736\text{ cm}^{-1}$ ) [5–7] increased with an increase in the polarisation angle. Due to the parallel orientation of these side groups in xylan, an orientation parallel to the longitudinal CW axis is indicated (Figure 3 right). For the lignin, the characteristic band signal ( $1517\text{ cm}^{-1}$ ) [8,9] decreased with an increase in the polarisation angle (Figure 3 right), indicating that lignin is organised in parallel with the longitudinal CW axis.

#### 4. Conclusion

It has been shown that xylan is oriented in parallel to the cellulose and more or less parallel to the axis of a cell wall, in isolated CW fragments from maize leaves. There was also a clear indication of lignin orientation parallel to the longitudinal CW axis. This means that all of these components show strong anisotropic behaviour and organisation.

#### Acknowledgement

*This work was supported by Ministry of Education, Science and Technological development of Republic Serbia (Project no. 173017, 45012) and COST Action FP0802.*

#### References

- [1] M. Pauly, K. Keegstra, *Plant J*, 54 (2008) 559–568
- [2] A.J. Ragauskas, C.K. Williams, B. H. Davison, *et al.*, *Science*, 311 (2006) 484–489
- [3] J. S. Stevanic, L. Salmén, *Holzforschung*, 63 (2009) 497–503
- [4] M. Chen, A.J. Sommer, J.W. McClure, *Phytochem. Anal*, 11 (2000) 153–159
- [5] R.H. Marchessault, *Pure Appl. Chem*, 5 (1962) 107–129
- [6] R.H. Marchessault, C. Y. Liang, *J. Polym. Sci*, 59 (1962) 357–378
- [7] M. Åkerholm, B. Hinterstoisser, L. Salmén, *Carbohydr. Res*, 339 (2004) 569–578
- [8] R.H. Atalla, U.P. Agarwal, *Science*, 227 (1985) 636–638
- [9] O. Faix, *Holzforschung*, 45 (1991) 21–27